arXiv:cond-mat/0510415v1 [cond-mat.supr-con] 16 Oct 2005

Slow transverse relaxation of the Zn-neighbor Cu nuclear spins in $YBa_2(Cu_{1-x}Zn_x)_4O_8$

Y. Itoh
Department of Chemistry, Graduate School of Science,
Kyoto University, Kyoto 606-8502, Japan

(February 2, 2008)

An explanation is given for the recent observation in the plane-site Cu nuclear quadrupole resonance (NQR) study of a heavily Zn-substituted $YBa_2(Cu_{1-x}Zn_x)_4O_8$ that the Cu nuclear spin-spin relaxation time T_{2G} near the impurity Zn is longer than that away from Zn. The long T_{2G} of the Zn-neighbor Cu nuclear spins results from a distant coupling between only a few nuclear spins near Zn, which does not indicate the absence of local enhancement of the staggered spin susceptibility around Zn.

74.25.Nf, 74.72.Bk, 76.60.-k

The Zn-induced local magnetic correlation in impurity Zn-substituted high-T_c superconductors has attracted great interests and brought about a lot of debates. In Refs.[1,2], it was debated whether the local magnetic correlation near Zn is enhanced or suppressed. Recently, in Refs.[3,4], it was debated whether the local staggered spin susceptibility is enhanced near Zn or literal local moments are induced.

In Ref.[4], Williams *et al.* criticized our Cu NQR study [5] for lightly Zn-substituted $YBa_2(Cu_{1-x}Zn_x)_4O_8$ (Y1248), using their NQR results for heavily Zn-substituted samples. Williams *et al.* criticized the site assignment of the satellite Cu NQR signals to the fourth nearest neighbor Cu sites about Zn. Actually, we assign the satellite signals to the *fraction* of the fourth nearest neighbor Cu sites in Y1248 [5]. They assigned the satellite NQR signals to the first nearest neighbor Cu sites and claimed that the local magnetic correlation near Zn is not enhanced, because they observed a weak frequency dependence of Cu nuclear spin-lattice relaxation time T_1 and a longer Cu nuclear spin-spin relaxation time T_{2G} at the satellite than that at the main NQR signals.

We have already reported a nonmonotonic change in the spin correlation from lightly to heavily Zn-substitution regimes [7] and the strong frequency dependence of T_1 for the lightly Zn-substituted Y1248 [5]. Already-existing reports indicate that the absence of rapid enhancement of transverse relaxation rates of the observable nuclear spins is the characteristic of the wipeout effect on Zn-substituted high-T_c superconductors [8–11]. The wipeout effect results from primarily a low frequency anomaly of the dynamical spin susceptibility related to the T_1 process but not necessarily a high frequency anomaly related to the static staggered spin susceptibility and T_{2G}. For the heavily Zn-substituted Y1248, the antiferromagnetic network on the CuO_2 plane is partly disconnected by the nonmagnetic impurities, so that the local magnetic correlation is also suppressed. It is likely that in the heavily Zn-substituted Y1248, a part of Zn impurities is substituted for the chain Cu site, because we have already observed the partial substitution effect by the chain-site Cu NQR experiments (not shown here). Technically, the satellite and the main Cu NQR spectra may be so broad and indistinguishable in the frequency dependence of T_1 for the heavily Zn-substituted Y1248 [6].

Although Williams *et al.* [4] criticize our model using binomial distribution functions [5] for being ”a complicated statistical model” and the impurity-induced NMR relaxation theory for being ”a nonunique model,” these criticisms are irrelevant, because the model and the theory have given satisfactory results for dilute alloys and dilute Heisenberg systems so far. Shortcomings of these analyses for the high-T_c superconductors as well as the quantum spin systems have already been recognized and totally discussed before.

In this paper, we focus on the unsolved problem in [6]; the reason why the slow nuclear spin-spin relaxation at the satellite Cu NQR lines was observed in the Zn-substituted Y1248 and how it is compatible with the local enhancement of staggered spin susceptibility around Zn. One should note that the literal local moments induced at the first nearest neighbor Cu site about Zn [4] is not compatible with the slow nuclear spin-echo decay [6] even if the absence of the local enhancement of the staggered spin susceptibility. Because the I_z-fluctuation due to a short T_1 and the Curie magnetism must enhance the nuclear spin-echo decay rate.

First, let us review how the Cu nuclear spin-spin relation rate $1/T_{2G}$ is expressed by the staggered spin susceptibility $\chi(\mathbf{Q})$ ($\mathbf{Q}$=[π, π]) in the high-T_c superconductors. The Cu nuclear spin-spin Hamiltonian [12,13] is expressed by

$$H_{II} = \sum_{i\neq j} a_{ij} I_{iz} I_{jz}. \tag{1}$$

Here, we neglect the effect of I_z-fluctuation by a short T_1 [14]. A range function a_{ij} between the nuclear spins I_i and I_j [13,15] is given by

$$a_{ij} = \int d\mathbf{q} \mathrm{A}^2(\mathbf{q}) \mathrm{Re}\chi(\mathbf{q}) \exp(\mathrm{i}\mathbf{q}\cdot\mathbf{r}_{\mathrm{ij}}), \tag{2}$$

where $A(\mathbf{q})$ is the Fourier transform of the hyperfine coupling constants between a nuclear and an electron spins. The high-T_c superconductors are considered to be quasi-two dimensional, nearly antiferromagnetic electron systems. The static spin susceptibility $\chi(\mathbf{q})$ is enhanced at or around the antiferromagnetic wave vector $\mathbf{q}$=$\mathbf{Q}$. Using the dynamical spin susceptibility $\chi(\mathbf{q},\omega)$ in [16,17], we obtain the range function [15]

$$a_{ij} \propto A^2(\mathbf{Q})\chi_0(\mathbf{Q})\sqrt{\frac{\xi}{r_{ij}}}\exp(-\frac{r_{\rm ij}}{\xi}), \tag{3}$$

where ξ is an antiferromagnetic correlation length, $\chi_0(\mathbf{Q})$ is the staggered spin susceptibility of bare electron gas, and $\chi(\mathbf{Q})$=$\chi_0(\mathbf{Q})(\xi/q_{\rm B})^2/\alpha_s A$ ($q_{\rm B}$ is the cut off wave vector, α_s is the exchange enhancement factor, and A is $|\partial^2\chi_0(\mathbf{q})/\partial\mathbf{q}^2|_{\mathbf{q}=\mathbf{Q}}/\chi_0(\mathbf{Q}))$ is given in [17]. For Y1248, we estimated ξ $\sim$3.4a (a is an in-plane lattice constant) at 100 K [18,19].

For simplicity, we assume a nuclear spin I=1/2 system. For the nuclear spins away from the impurities, the nuclear spin-spin relaxation curve $E(2\tau)$ as a function of time τ in a sequence of $\pi/2$-τ-π pulses is given by

$$E(2\tau) = E_0\prod_{j=1}\cos(2a_{\rm ij}\tau) \tag{4}$$

$$\approx E_0\exp[-\frac{(2\tau)^2}{2}\sum_{\rm j=1}a_{\rm ij}^2], \tag{5}$$

[12,20–22]. Using eq.(2) or (3), we obtain the square of the Gaussian relaxation rate of nuclear spin-echo decay

$$\Big(\frac{1}{T_{\rm 2G}}\Big)^2 = \sum_{j=1}^{\infty}a_{0j}^2 \propto A^4(\mathbf{Q}){\rm Re}\chi(\mathbf{Q})^2, \tag{6}$$

[15,23–25]. One should note that eq. (6) is not applicable to a finite spin system, in which a few nuclear spins are distantly coupled with each other. e.g. the first and the fourth nearest neighbor Cu spins around Zn. The satellite Cu NQR corresponds to such a system. Unfortunately, Williams *et al.* applied eq. (6) to the satellite Cu nuclear spin-echo decay [4,6].

For the first nearest neighbor Cu nuclei around Zn, we obtain

$$\Big(\frac{1}{{}^{\rm 1st}T_{\rm 2G}}\Big)^2 \approx \sum_{k=1}^{2}a_{1k}^2, \tag{7}$$

where k belongs to the 1st nearest neighbor Cu sites around Zn. Figure 1 illustrates the CuO$_2$ plane with an impurity Zn. For the fourth nearest neighbor Cu nuclei around Zn, we obtain

$$\Big(\frac{1}{{}^{\rm 4th}T_{\rm 2G}}\Big)^2 \approx \sum_{l=1}^{6}a_{4l}^2, \tag{8}$$

where l belongs to the 4th nearest neighbor Cu sites around Zn.

Not $\chi(\mathbf{Q})$ in eq. (6) but eq. (3) should be taken into consideration for the first and the fourth nearest neighbor Cu nuclear spins. Equations (7) and (8) are the finite lattice sums of the square of the range function of eq. (3). In rough estimation of eqs. (7) and (8) from eq. (3), since ξ $\sim$3.4a and assuming $a_{0j} \approx a_{1j} \approx a_{4j}$, then about 36 nuclear spins contribute eq. (6), whereas only 2 spins contribute eq. (7) and about 6 or less spins contribute eq. (8). Thus, we obatin

$$\Big(\frac{1}{T_{\rm 2G}}\Big)^2 >> \Big(\frac{1}{{}^{\rm 1st}T_{\rm 2G}}\Big)^2, \Big(\frac{1}{{}^{\rm 4th}T_{\rm 2G}}\Big)^2. \tag{9}$$

If the satellite Cu NQR signals are assigned to the first nearest neighbor Cu sites as in [4], the spin-echo modulation of $\cos^2(2a_{k1}\tau)$ must be observed but has never been reported. Thus, the slow nuclear spin-spin relaxation does not indicate the absence of the enhancement of the local staggered spin susceptibility around Zn but rather supports our site assignment of the satellite Cu NQR signals to a part of the fourth nearest neighbor Cu sites [5] even for the heavily Zn-substituted Y1248.

Eventually, the problem is how much the local staggered spin susceptibility in a_{4l} and a_{1k} is enhanced around Zn. The detailed measurements of $T_{\rm 2G}$ of the satellite Cu NQR signals for the lightly Zn-substituted Y1248 might be a theoretical constraint on modeling the staggered susceptibility about Zn.

ACKNOWLEDGMENTS

I would like to thank T. Machi and K. Yoshimura for their stimulating discussions. This study was supported by a Grant-in-Aid for Science Research on Priority Area, 'Invention of anomalous quantum materials' from the Ministry of Education, Science, Sports and Culture of Japan (Grant No. 16076210).

[1] H. Alloul, J. Bobroff, and P. Mendels, Phys. Rev. Lett. **78**, 2494 (1997).
[2] K. Ishida, Y. Kitaoka, and K. Asayama, Phys. Rev. Lett. **78**, 2495 (1997).
[3] M.-H. Julien, T. Tokunaga, T. Fehér, M. Horvatić, and C. Berthier, Phys.Rev. B **71**, 176501 (2005).
[4] G. V. M. Williams, S. Krämer, J. L. Tallon, R. Dupree, and J. W. Loram, Phys. Rev. B **71**, 176502 (2005).
[5] Y. Itoh, T. Machi, C. Kasai, S. Adachi, N. Koshizuka, and M. Murakami, Phys. Rev. B **67**, 064516 (2003).
[6] G. V. M. Williams, and S. Krämer, Phys. Rev. B **64**, 104506 (2001).

[7] Y. Itoh, T. Machi, N. Watanabe, S. Adachi, and N. Koshizuka, J. Phys. Soc. Jpn. **70**, 1881 (2001).

[8] A. W. Hunt, P. M. Singer, A. F. Cederström, and T. Imai, Phys. Rev. B **64**, 134525 (2001).

[9] Y. Kobayashi, T. Miyashita, M. Ambai, T. Fukamachi, and M. Sato, J. Phys. Soc. Jpn. **70**, 1133 (2001).

[10] H. Yamagata, H. Miyamoto, K. Nakamura, M. Matsumura, and Y. Itoh, Physica C **388-389**, 259 (2003).

[11] H. Yamagata, H. Miyamoto, K. Nakamura, M. Matsumura, and Y. Itoh, J. Phys. Soc. Jpn. **72**, 1768 (2003).

[12] C. H. Pennington, D. J. Durand, C. P. Slichter, J. P. Rice, E. D. Bukowski, and D. M. Ginsberg, Phys. Rev. B **39**, 274 (1989).

[13] C. H. Pennington and C. P. Slichter, Phys. Rev. Lett. **66**, 381 (1991).

[14] N. J. Curro, T. Imai, C. P. Slichter, and B. Dabrowski, Phys. Rev. B **56**, 877 (1997).

[15] Y. Itoh, H. Yasuoka, Y. Fujiwara, Y. Ueda, T. Machi, I. Tomeno, K.Tai, N.Koshizuka, and S. Tanaka, J. Phys. Soc. Jpn. **61**, 1287 (1992).

[16] A. Millis, H. Monien, and D. Pines, Phy. Rev. B **42**, 167 (1990).

[17] T. Moriya, Y. Takahashi, and Y. Ueda, J. Phys. Soc. Jpn. **59**, 2905 (1990).

[18] Y. Itoh, J. Phys. Soc. Jpn. **63**, 3522 (1994), *ibid.* **64**, 684 (1995).

[19] Y. Itoh, A. Hayashi, and Y. Ueda, J. Phys. Soc. Jpn. **64**, 3074 (1995).

[20] J. Ph. Ansermet, C. P. Slichter, and J. H. Sinfelt, J. Chem. Phys. **88**, 5963 (1988).

[21] C. P. Slichter, *Principles of Magnetic Resonance*, (Springer-Verlag, Tokyo 1990).

[22] A. Abragam, *The Principles of Nuclear Magnetism*, (Clarendon Press, Oxford 1986).

[23] Y. Itoh, K. Yoshimura, T. Ohmura, H. Yasuoka, Y. Ueda, and K. Kosuge, J. Phys. Soc. Jpn. **63**, 1455 (1994).

[24] D. Thelen and D. Pines, Phys. Rev. B **49**, 3528 (1994).

[25] M. Takigawa, Phys. Rev. B**49**, 4158 (1994).

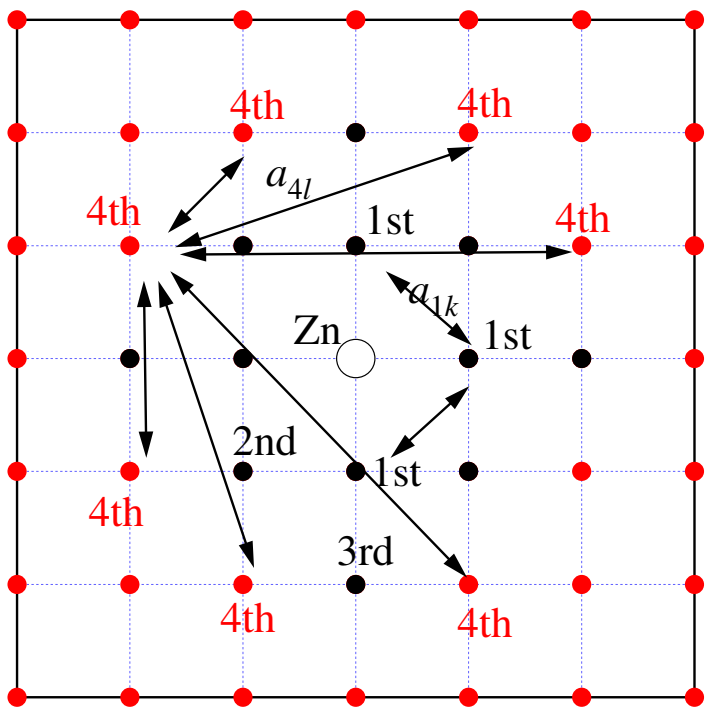

FIG. 1. Top view of a CuO_2 plane with a Zn impurity (an open circle). Closed circles are the Cu ions. Oxygen ions are omitted. The arrows indicate the pairs of nuclear spin-spin coupling. a_{1k} (k=1, 2) is the coupling constants between the first nearest neighbor Cu nuclear spins about Zn and a_{4l} (l=1, 2, $\cdots$, 6) is those between the fourth nearest neighbor Cu nuclear spins about Zn.